

Evaluative Study On Blended Concrete Using Copper Slag And Silica Fume As A Partially Replacement Material

Adhav Madhuri Kisan¹, Shirsath Mohan², Ayan S.Gupta³

^{1,2,3} Department of Civil Engineering

^{1,2} G.H.R.C.O.E. & M. Chas, Ahmednagar,

³ P.D.V.V.P.C.O.E. Vilad Ghat, Ahmednagar.

Abstract- As in today's Industrial waste is used to make cement and concrete in the constructional field. New by-products and waste material are produced in the industry. Damping or Disposal of these materials causes environmental as well as health problems There is a lot of potential in the concrete industry to recycle waste material. high performance concrete is technically and economically very helpful due to it's used in massive volumes. This Study faces on the Strength performance of concrete with copper slag, silica fume and it's blend. cement & Sand replacement by Various percentage with copper slag, silica fume and it's blend are studied. Concrete tests are conducted on the concrete samples at the specific ages. The comparison made on the basis of compressive and tensile strength performance of copper slag and silica fume. Respective graphs and discussion will be made to find out the optimum result and make it more sustainable product to be used for the construction.

Keywords- Copper slag, Silica Fume, Blended concrete, compressive strength, split tensile strength.

I. INTRODUCTION

Concrete is the most widely used construction material in all over the world. Aggregates are the most important component of concrete and about 42 % of 15 billion tons of aggregates Produced each year are used in concrete, of which only 8 % are recycled aggregates. There is a lot of potential in the concrete industry to recycle waste material. For many years, by-products such as fly ash, silica fume and slag were considered as waste materials. Due to this the concrete improved its workability and durability compared to normal Concrete and has been used in the construction of power, chemical plants and under-water structures. The waste material such as copper slag which can used as partial or full substitute of either cement or aggregates. It is a by- product obtained during the matte smelting and refining of copper Approximately 2.2–3.0 tons copper slag is generated as a by-product material to produce every ton of copper. This slag is

currently being used for many applications like land filling, grit blasting, etc. and utilizes only about 15–20 % of the copper slag generated. Silica fume is used as an admixture or replacement of cement and other concrete constituents. It is an ultrafine powder collected as a by-product of silicon and Ferrosilicon alloy production which can be readily used as a replacement for cement thus reducing the effect of Portland cement. The researches shows that the silica fume have a beneficial influence on strength and durability of reinforced concrete. When pozzolanic materials are incorporated to concrete, the silica present in these materials reacts with thecalcium hydroxide released during the hydration of cement and forms additional calcium silicate hydrate (C-S-H),which improve the mechanical properties of concrete.

II. LITERATURE REVIEW

A. Katz et.al.[1] Concluded That The role of silica-fume agglomerates, found in densified silica-fume (DSF) pastes, in the immobilization mechanism of Cs ions was studied. this work suggests that during the pozzolanic reaction, a hydrated rim develops around the agglomerate that acts as an additional diffusion barrier for the Cs ions, resulting in an increased efficiency of Cs immobilization.

Rizwan et.al.[2] says The current research is aimed to investigate the sustainable utilisation of CS as fine aggregates in Self Compacting Concrete (SCC) using fly ash (FA) and silica fume (SF) as Supplementary Cementitious Materials (SCMs). The results of scanning electron microscopy and energy dispersive spectroscopy illustrate the formation of uniformly distributed and compact C-S-H gel in presence of CS after 120 d, with Ca/Si ratio ranging between 0.77 and 1.11. The SCC mix with 100% CS substitution was found to be most economical with least consumption of embodied energy and emission of embodied carbon dioxide. This study authenticates that CS in combination with SCMs is promising alternative over the conventional sand in construction industry.

Andrade et.al [3] Concluded that The present work focuses on assessing the viability of applying blasted copper slag, produced during abrasive blasting, as fine aggregate for Portland cement concrete manufacturing, Assays showed a significant improvement in workability, with the increase in substitution offline aggregate. With 80% of replacement, the concrete presented lower levels of water absorption capacity. Axial compressive strength and diametrical compressive strength decreased, with the increase of residue replacement content. The greatest reductions of compressive strength were found when the replacement was over 40%. For tensile strength by diametrical compression.

Al-jabri et al [4] Concluded that the effect of using copper slag as a fine aggregate on the properties of cement mortars and concrete. Various mortar and concrete mixtures were prepared with different proportions of copper slag ranging from 0% (for the control mixture) to 100% as fine aggregates replacement. addition of more copper slag resulted in strength reduction due to the increase in the free water content in the mix. The results demonstrated that surface water absorption decreased as copper slag content increases up to 50% replacement. Beyond that, the absorption rate increased rapidly and the percentage volume of the permeable voids was control mixture.

III. EXPERIMENTAL WORK

The materials used are :

1. Cement – Here we used Ordinary Portland cement 53 grade used.
2. Silica Fume - Silica fume is produced during a high-temperature reduction of quartz in an electric arc
3. Furnace when the main product is silicon or ferrosilicon. The chemical process is complex and it depends on the temperature of the producing.
4. Copper Slag - Copper slag is a by-product material produced from the process of manufacturing copper. As the copper settles down in the smelter. The end product is a solid, hard material that goes to the crusher for further processing. Copper slag used in this work was bought foam Ujjwal industries (India) Pvt.ltd, Ahamednagar, India.
5. Fine aggregates - Locally available sand was used as fine aggregate. The specific gravity of fine aggregate is 2.63
6. Coarse aggregates - Crushed granite metal with 12.5 mm and retained on 10 mm sieve was used and also 20 mm was used. The sieve analysis of the aggregates was carried out and the same distribution

Table 1. Physical Properties of copper slag

Physical Properties	Copper Slag
Particle shape	Irregular
Appearance	Black and glassy
Type	Air cooled
Specific gravity	3.91
Percentage of voids %	35
Bulk density g/cc	2.08
Fineness Modulus	3.47
Angle of internal friction	51° 20"
Fineness m ² /kg (after grinding)	125
Moisture content %	0.1
Water absorption %	0.16
Ultimate shear stress kg/cm ²	2.08

Table 2. Chemical Properties of copper slag as per Ujjwal Industries Pvt. Ltd..

Sr.no.	Chemical Component	% of Chemical Component
1.	SiO ₂	25.84
2.	Fe ₂ O ₃	68.29
3.	Al ₂ O ₃	0.22
4.	CaO	0.15
5.	Na ₂ O	0.58
6.	K ₂ O	0.23
7.	Mn ₂ O ₃	0.22
8.	TiO ₂	0.41
9.	SO ₃	0.11
10.	CuO	1.20
11.	Sulphide sulphur	0.25

Table 3. Properties Of Silica fume as per Yonsons Eng. Pvt. Ltd

Properties	Results
SiO ₂	>97%
SO ₃	0.4
Al ₂ O ₃	0.5%
Colour	Premium white
Specific gravity	2.2
Particle size	1μ
Bulk density	576 kg/m ³
Surface area	20000 m ² /kg
Fineness	3 %

IV. EXPERIMENTATION AND TESTS

Mix Proportioning:-

The mix design is done according to the IS design method Concrete Mixes In this study, the early age properties of fresh concrete and mechanical performance and tensile strength of hardened concrete were examined. All tests were conducted using the following sample groups:

- 1) An ordinary cement paste or concrete,
- 2) Pastes or concrete substituted with 6%, 8%, 10%, 12% SF by mass of cement
- 3) Pastes or concrete substituted with 5%, 10%, 15%, 20% CS by mass of sand

Mixing procedure

The mixing procedures are divided into three stages. In the first stage, all the binders (cement, silica fume, copper slag) were weighted accordingly and mixed by hand until all the constituents mixed uniformly. This is to make sure all the binders are mixed thoroughly to produce a homogenous mix. The second stage involves mixing the binders with the aggregates for about 5 minutes. At the final stage, measured water is added into the concrete mix. This step is crucially important to make sure that the water is distributed evenly so that the concrete will have similar water-binder ratios for every cube. After that, the concrete was then poured into the mould. Preparing test cubes

The size of the mould is 150 x 150 x150 mm used to produce the 30 cubes were used for each concrete mix. The concrete was poured into the mould in two layers where each layer was compacted using a steel bar. The cubes were removed from the moulds after 24 hours and cured using sacks in room temperature.

Preparing test cylinders

The size of cylinder used for split tensile strength and durability studies was 150mm diameter and 300mm height. This test was conducted in accordance with IS: 5816-1999. The crude oil was applied along the inner surfaces of the mould for the easy removal of specimens from the mould. Concrete was poured throughout its length and compacted well.

Curing

In this study cubes were cured by dipping the specimen

In water 25°C at the end of 24 hours of casting after allowing for air drying.

Experimental procedures

Compressive strength test Concrete cubes of size 150mm×150mm×150mm were cast with and without copper slag. During casting, the cubes were mechanically vibrated using a table vibrator. After 24 hours, the specimens were demoulded and subjected to curing for 28 days in portable water. After curing, the specimens were tested for compressive strength using compression testing machine of 2000KN capacity. The maximum load at failure was taken. The average compressive strength of concrete and mortar specimens was

IV. RESULTS AND DISCUSSIONS

The Compressive Strength of M40 Concrete Specimen cube Testing Results Variation in 5%,10%,15%,20% replacement of Copper Slag and 6%,8%,10%,12% replacement of Silica fume are following:

Table 4. Compressive Strength Test of Replacement % of Silica Fume

% Replacement of Copper Slag	3days compressive strength	7days compressive strength	28days compressive strength
5%	23.5	31.03	44.63
10%	25.54	34.94	49.81
15%	25.89	36.44	52.14
20%	27.55	36.45	54.15

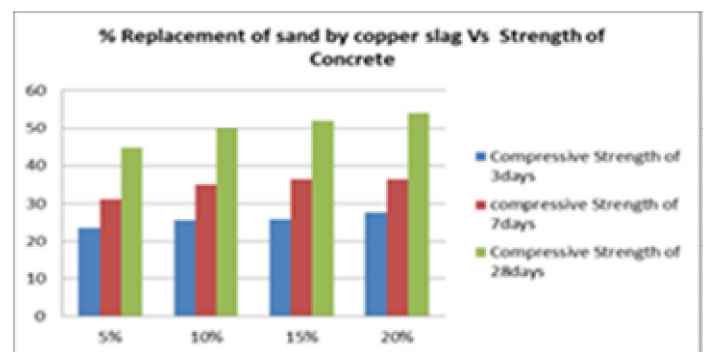


Figure 1. Compressive Strength result of partially replacement by Copper Slag for Sand in Concrete

Table 5. Flexural & Split Tensile Strength Test of Replacement % of Copper Slag

% Replacement of Copper Slag	28 Days Split Tensile Strength(N/mm2)	28 Days Flexural Strength(N/mm2)
5%	3.96	4.75
10%	4.7	4.9
15%	4.4	5.21
20%	4.45	5.78

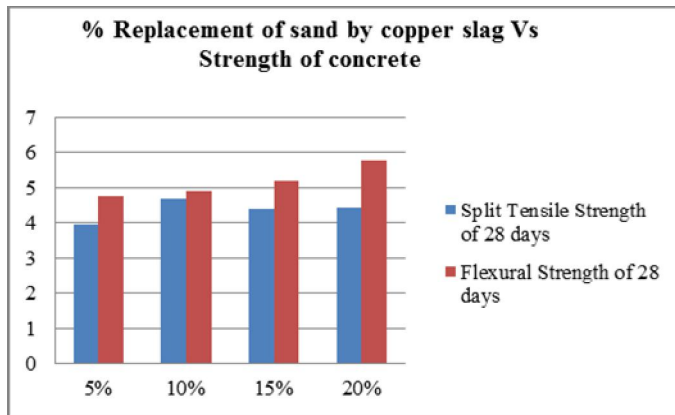


Figure 2. Split Tensile Strength & Flexural Strength Test result of partially replacement by Copper Slag for Sand in Concrete

Table 6. Compressive Strength Test of Replacement % of Silica Fume

% Replacement of Silica Fume	7days compressive strength(N/mm2)	28days compressive strength(N/mm2)
6%	29.46	41.89
8%	30.6	44.25
10%	33.66	48.89
12%	32.54	46.25

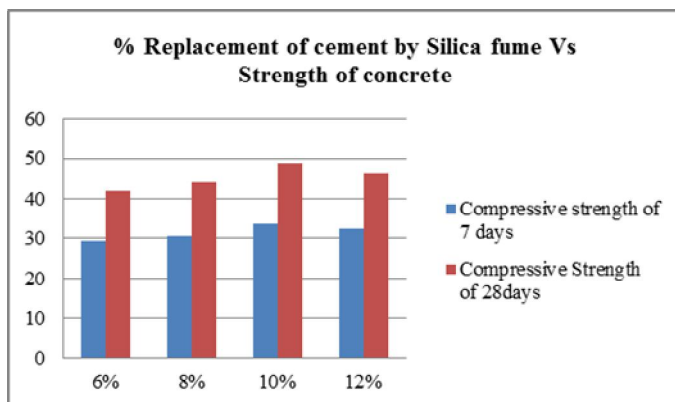


Figure 3. Compressive Strength result of partially replacement by Silica Fume for Cement in Concrete

Table 7. Flexural & Split Tensile Strength Test of Replacement % of Silica Fume

% Replacement of Silica Fume	28 Days Split Tensile Strength(N/mm2)	28 Days Flexural Strength(N/mm2)
6%	4.75	7.9
8%	5.24	9.5
10%	5.75	9.1
12%	4.43	8.13

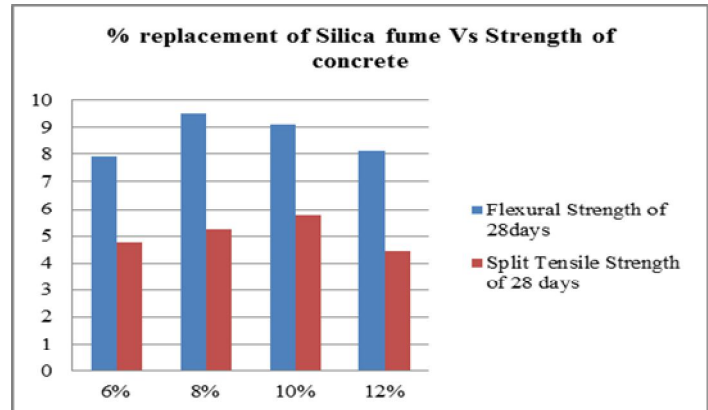


Figure 4. Split Tensile Strength & Flexural Strength Test result of partially replacement by Silica Fume for Cement in Concrete

V. CONCLUSION

From this paper we can conclude that,

1. It has been observed that maximum compressive strength is noted for 10% replacement of silica fume than normal concrete.
2. It has been observed that maximum compressive strength is
3. noted for 20% replacement of Copper Slag than normal concrete.
4. Consistency of cement depends upon its fineness. Silica fume is having greater fineness than cement and greater surface area so the consistency increases greatly, when silica fume percentage increases.
5. 4. The optimum 28-day Split Tensile and flexural strength have been obtained in range of 10-15 % silica fume replacement level.
6. 5. The optimum 28-day Split Tensile and flexural strength have been obtained in range of 10% silica fume replacement level.

REFERENCES

- [1] A. Katz, Y. Peled The Mechanism of www.ijart.com

cesium immobilization In densified silica fume blended cement paste, Volume 38

- [2] Rizwan A. Khan, Sustainable use of Copper Slag in self-Compacting concrete containing supplementary Cementitious materials, volume 151, May 2017, PP 179-192
- [3] N. Andrade, Blasted Copper Slag as Fine Aggregate in Portland Cement Concrete, Volume 196, July 2017, PP 607-613
- [4] Akihiko, Y. and Takashi, Y. "Study of utilization of copper slag as fine aggregate for concrete", Ashikaya Kogyo Daigaku Kenkyu Shuroku, Vol. 23, pp. 79-85, 1996.
- [5] Al-Jabri, K. and Makoto Hisada. "Copper slag as sand replacement for high performance concrete", Cement & Concrete Composites, Vol. 31, 483- 488, 2009
- [6] Al-Jabri, K.S., Abdullah, H., Al-Saidy and Ramzi Taha. "Effect of copper slag as a fine aggregate on the properties of cement mortars and concrete", Construction and Building Materials, Vol. 25, pp. 933-938, 2011.
- [7] Al-Jabri, K.S., Taha, R.A., Al-Hashmi, A. and Al-Harthy, A.S. "Effect of copper slag and cement by-pass dust addition on mechanical properties of concrete", Construction and building materials, Vol. 20, 322-331, 2006.
- [8] Wu, W., Zhang, W. and Ma, G. "Optimum content of copper slag as a fine aggregate in high strength concrete", Material design, Vol.31, No.6, pp. 2878
- [9] IS : 1727 – 1967, "Indian Standard methods of test for pozzolanic materials", Bureau of Indian standards, New Delhi.
- [10] IS 2386 : Part 3 : "Methods of Test for Aggregates for Concrete Part 3, 1963.
- [11] IS 4031: Part 4: "Methods for physical test for hydraulic cements", Bureau of Indian standards, New Delhi, 1988.
- [12] IS 516:1959, "Method of Test for Strength of Concrete"