

Replacement Of Fine Aggregates By Vermiculite In Concrete

Dr. T. Palani¹, Mrs. A.L. Mahalakshmi², J. Mohammed Althaf³, S.Vignesh⁴, V.Vignesh⁵, S.Mohamme Zuber Basha⁶, Mr K.Kaviarasn M.E.⁷

¹Professor, Dept of civil Engineering

^{2,7}Assistant Professor, Dept of civil Engineering

^{3,4,5,6}Dept of civil Engineering

^{1,2,3,4,5,6,7}T.J.S Engineering college, puduvoyal, gummidipoondi, Thiruvallur-601206

Abstract- Concrete is the single most widely used construction material in the world. Concrete is used in such large amounts because it is simply, a remarkably good building material. Aggregates generally occupy 60 to 80 percent of the volume of concrete and greatly influence its properties, mix proportions and economy. Use of vermiculite in concrete, enhances the shrinkage and crack resistance, fire resistance and reduces environmental impact and also reduces the cost. Important characteristics of a good quality aggregate include resistance to abrasion, resistance to freeze/thaw action, resistance to sulfates, correct shape and surface texture, proper gradation, density, and compressive and flexural strength. The main purpose of the research is to study the strength parameters such as compressive strength, split tensile & flexural strength of concrete using vermiculite as partial replacement with 50%, 60%, 75% and 100% by weight. The main aim of this study is to make economical and eco-friendly.

workability, improved fire resistance, improved resistance to cracking and shrinkage and mainly inert chemical nature. Vermiculites taken for concrete preparation which pass through 2.36mm sieve size (By reference 14).



Figure-1 Vermiculites passing through 2.36mm sieve

I. INTRODUCTION

As concrete is the good building material it is used world wide in various structural members such as slabs, beams, columns, foundation, etc. Due to its low thermal conductivity property, fine aggregates are replaced with vermiculite and its compressive strength are tested. Generally vermiculite can resist the temperature up to 1200°C and it has high thermal insulation co-efficient of $\lambda > 0.046 \text{ W/m}^\circ \text{C}$. Because of this property vermiculites are added in concrete by replacing fine aggregates by 50%, 60%, 75% and 100% by weight and their compressive strength are found (By reference 14). iendly concrete (By Reference 14)

II. MATERIALS USED

A. Vermiculite

Vermiculite is a hydrous phyllosilicate mineral. It undergoes significant expansion when heated. Vermiculite is chosen to replace fine aggregates in concrete because of its specific properties such as it is lighter in weight, improved

B. Cement

Cement used to prepare the specimen was 53 grade Ordinary Portland cement, conforming to IS 12269:2013 with a fineness of 1%, standard consistency of 34% and Initial setting time 80 min.

C. Course aggregates

Course aggregates of 4.75mm to 12.5mm size aggregates were used.

D. Fine aggregates

Fine aggregates are taken for concrete preparation which pass through 2.36mm sieve size

E. Water

Portable water was used for mixing and curing of concrete specimens.

III. MIX DESIGN

As per IS CODE BOOK design mix for M 25 grade of concrete was prepared by replacing fine aggregates by 50%, 60%, 75% and 100% by weight.

IV. MATERIALS TEST RESULT

Table-1 Physical properties of cement

Fineness Modulus	Normal consistency	Initial Setting time	Final Setting time
1.0	34%	80min	260 min

Table-2 Physical properties of fine aggregates

Fineness Modulus	Specific gravity	Water absorption
2.85	3.1	1.92

Table-3 Physical properties of Vermiculites

Fineness Modulus	Specific gravity	Water absorption
2.46	3.80	2.65

Table-4 Physical properties of Coarse aggregates

Fineness Modulus	Specific gravity	Water absorption
7.73	2.7	1.5

IV. TEST RESULTS

A. Compressive Strength

Compressive strength was tested in compressive testing machine .Cube specimens of size 150mm x 150mm x 150mm were adopted for the test. Compressive strength was tested after 7,21 and 28 days of curing. The results of the tests are tabulated below.

Table-5 Compressive strength of 50% vermiculite replacing concrete

Age of curing	Average strength
7	18
21	24
28	27.5

Table-6 compressive strength of 60%vermiculite replacing concrete

Age of curing	Average strength
7	19.1
21	25
28	29

Table-7 – compressive strength of 75% vermiculite concrete

Age of curing	Average strength
7	14
21	20
28	21.5

Table-8 compressive strength of 100% vermiculite concrete

Age of curing	Average strength
7	13
21	17
28	20

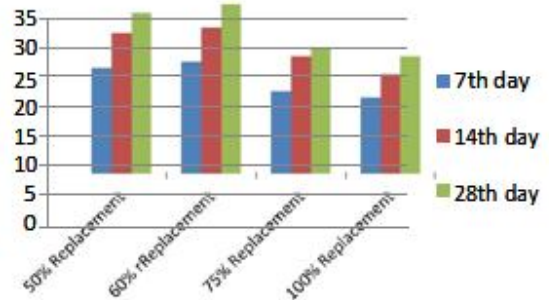


Figure 2 – test results are clearly shown in graph

V. CONCLUSIONS

- The compressive strength of vermiculite concretes of various percentages are found.
- The optimum strength in comparing the strengths for different vermiculite was observed to be 50%.and 60%.
- Addition of vermiculites in concrete makes it heat resisting & resists shrinkage and cracks in concrete.
- Because of inert chemical nature of vermiculite when it is used in concrete it will not undergo any chemical reaction and also it is an eco-friendly material.
- But, 60% replacement is only possible. total replacement of vermiculite in concrete is not possible

REFERENCES

- [1] Dushyant Rameshbhai Bhimani (2013) “Used Foundry Sand: Opportunities For development Of Eco-friendly Low Cost Concrete” Journal of Advanced Engineering Technology.
- [2] Dushyant R. Bhimani (2013) “A Study on Foundry Sand: Opportunities for Sustainable and Economical Concrete” Journal of Building Physics.
- [3] Dushyant R. Bhimani (2013) “Innovative Ideas for Manufacturing of the Green Concrete by Utilizing the Used Foundry Sand” Journal of Emerging Science and Engineering
- [4] Manolia Abed Al-wahab Ali (2012) “The Possibility of Produce Self Compacted Polystyrene Concrete” Journal of Engineering and Development.
- [5] Eknath P.Salokhe, D.B.Desai (2012) “Application of Foundry Waste Sand In Manufacture of Concrete” Jurnal of Mechanical and Civil Engineering.
- [6] Hind M.Ewadh, Noorezlin A. Basri (2012) “Effectiveness of Polystyrene Beads as Aggregate Replacement Material to Recycle Solid Waste” Journal of Scientific & Engineering Research.
- [7] K.Rajeshkumar, N.Mahendran,R. Gobinath (2010) “Experimental Studies on Viability of Using Geosynthetics as Fibres in Concrete” International Journal Of Applied Engineering Research.
- [8] Youjiang Wang et al (2000) “Concrete Reinforcement With Recycled Fibers” Journal Of Materials In Civil Engineering.
- [9] Journal of the International Hemp Association. Vol. 1 (1994)–Vol. 6 (1999).
- [10] IS 456- 000 “Plain and reinforced concrete code of practice”.
- [11] IS 10262 - 009 “Recommended guidelines for concrete mi design”.
- [12] Shetty.M.S (2005), “Concrete Technology Theory and Practice” S.Chand & Co, ltd., published in New Delhi.
- [13] Santa Monica green concrete guidelines
- [14] S. Syed Abdul Rahuman and Gijo K Babu at 2016, replace fine aggregate by vermiculite by 0% ,5% and 10%.